

Short paper

Open Access

A biocompatible magnetic film: synthesis and characterization

Jhunu Chatterjee, Yousef Haik* and Ching Jen Chen

Address: Center for Nanomagnetism and Biotechnology, Florida State University, Tallahassee, Florida 32310, USA

Email: Jhunu Chatterjee - jhunu@eng.fsu.edu; Yousef Haik* - haik@eng.fsu.edu; Ching Jen Chen - cjchen@eng.fsu.edu

* Corresponding author

Published: 04 February 2004

Received: 21 January 2004

BioMagnetic Research and Technology 2004, 2:2

Accepted: 04 February 2004

This article is available from: <http://www.biomagres.com/content/2/1/2>

© 2004 Chatterjee et al; licensee BioMed Central Ltd. This is an Open Access article: verbatim copying and redistribution of this article are permitted in all media for any purpose, provided this notice is preserved along with the article's original URL.

Abstract

Background: Biotechnology applications of magnetic gels include biosensors, targeted drug delivery, artificial muscles and magnetic buckles. These gels are produced by incorporating magnetic materials in the polymer composites.

Methods: A biocompatible magnetic gel film has been synthesized using polyvinyl alcohol. The magnetic gel was dried to generate a biocompatible magnetic film. Nanosized iron oxide particles ($\gamma\text{-Fe}_2\text{O}_3$, ~7 nm) have been used to produce the magnetic gel.

Results: The surface morphology and magnetic properties of the gel films were studied. The iron oxide particles are superparamagnetic and the gel film also showed superparamagnetic behavior.

Conclusion: Magnetic gel made out of crosslinked magnetic nanoparticles in the polymer network was found to be stable and possess the magnetic properties of the nanoparticles.

Background

Polyvinyl alcohol (PVA) is a unique synthetic biocompatible polymer and it has a large number of hydroxyl groups that can react with many kinds of functional groups. Apart from its different industrial uses, it is widely being used in sensors and in drug delivery system [1,2]. Ferrogels made with PVA can mimic artificial muscle [3]. Synthesis of PVA magnetic fiber which can be used as magnetic paper, health care cloth or electromagnetic wave absorbent has been recently reported [4]. Here we report a synthesis of a PVA magnetic film generated from PVA magnetic gel. This film can be useful as sensors in biomedical applications. We used a two step synthesis process for generating the magnetic gel [3]. Nanosized iron oxide particles ($\gamma\text{-Fe}_2\text{O}_3$, ~7 nm) have been used to make the magnetic gel. The magnetic gel was dried to generate biocompatible magnetic films of different thicknesses. The surface morphology and magnetic properties of the gel films were also studied. The iron oxide particles are superparamagnetic and the gel film also showed superparamagnetic behavior.

Methods

Polyvinyl alcohol polymers ($M_w = 25,000$ and $125,000$) were obtained from Polysciences, Inc. Glutaraldehyde and nitric acid were obtained from Sigma Chemical Company.

A two-step process was used to form the magnetic gel film. In the first step, surface modified nanosized maghemite was synthesized. The second step was the formation of composite materials. Maghemite was formed by conventional coprecipitation process [5] using ferrous chloride and ferric chloride in 1:2 molar ratios. We have used ultrasonication along with coprecipitation process. Later on the surface of the maghemite was modified with a cationic surfactant, cetyltrimethylammonium bromide [6].

In the second step different concentrations (2–5%) of two different polyvinyl alcohol polymers ($M_w = 25,000$ and $125,000$) were made in water. The surface modified maghemite was then added in different weight proportions (20–50% of the weight of polymer) and sonicated at

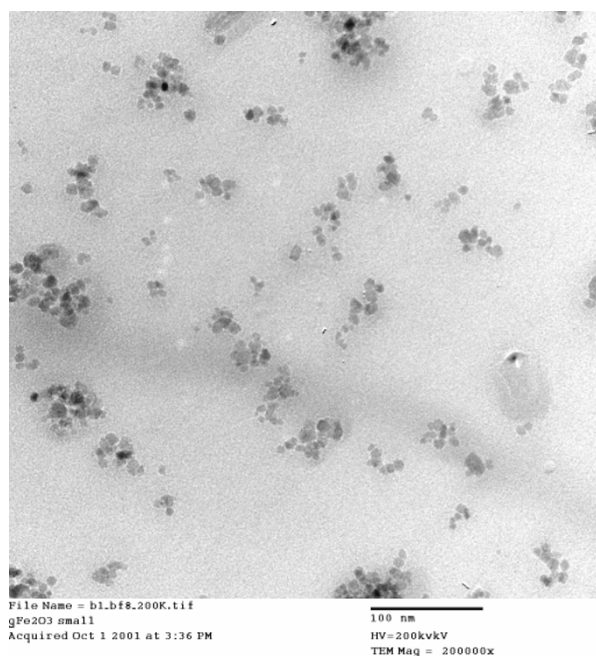


Figure 1
TEM micrograph for maghemite ($\gamma\text{-Fe}_2\text{O}_3$) particles

50% amplitude for 30 s. Glutaraldehyde was used as crosslinking agent (at slightly acidic pH, about 6) using 1 M nitric acid. Formation of gel occurred almost immediately. The crosslinking density was varied by using different amounts of glutaraldehyde. The gels were formed in rectangular aluminum trays and dried. The gels were dried till they formed a film of constant weight ensuring the absence of water.

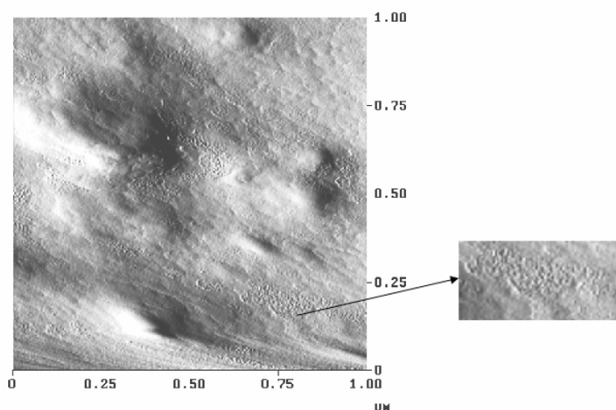


Figure 2
AFM micrograph for PVA magnetic film

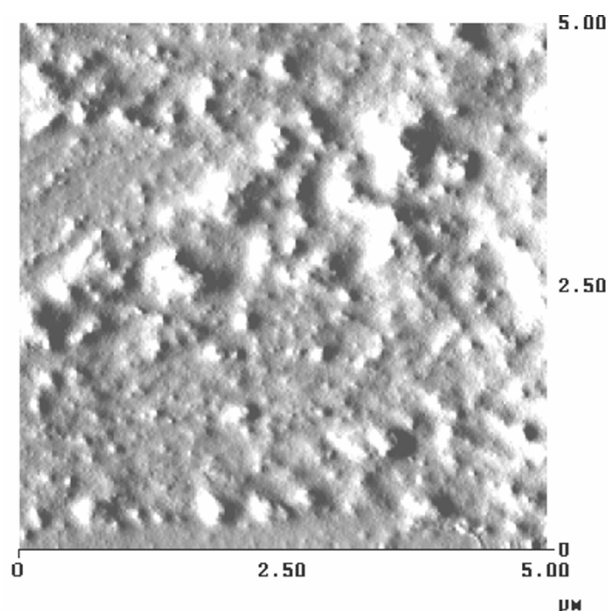


Figure 3
AFM micrograph for PVA magnetic gel

Results and Discussion

The size and the shape of the surface modified maghemite particles were determined by transmission electron microscopy (JEOL STEM 2010). The micrograph is shown in Fig. 1. The particles are in the size range of 7 – 10 nm and have fairly uniform distribution. These particles are superparamagnetic in nature as reported earlier [6].

The surface property of these gel films was studied by atomic force microscopy. A thin film was put on a glass slide to observe under the Atomic force microscope (D 3000, Digital Instruments, Santa Barbara). PVA film formed lamellar structures as observed in the micrograph (Fig. 2). Crystalline structure must have formed in the gel itself though it was not clearly observed when microscopy was done on a gel sample and it showed a globular and porous structure along with contrast due to the presence of maghemite in them. The surface of the gel film shows the presence of iron oxide particles in the matrix as observed in the AFM micrograph (Fig. 3).

The magnetic property of the gel was measured by a Superconducting Quantum Interference Device (MPMS 5, Quantum Design). Magnetization measurement was done at 300 K and at 5 K. A small piece of PVA magnetic film was placed in a gelatin capsule and inserted in the SQUID. There is almost no remnant magnetization at 300 K but at 5 K, hysteresis loop was observed (Fig 4). This

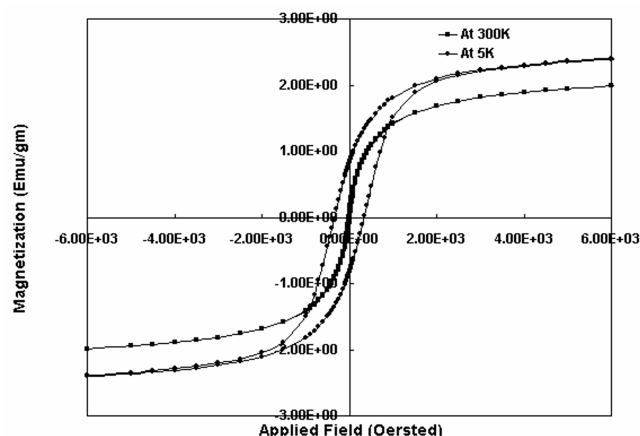


Figure 4
Hysteresis plot for PVA magnetic film

shows that the superparamagnetic nature of the nano-sized maghemite particles [7, 8] did not change in presence of the polymer network and the composite film itself behaved as a superparamagnetic material.

Conclusions

A biocompatible magnetic film has been generated from the gel. As a crosslinked gel forms a three dimensional network the film formed from is expected to have more tensile strength than the solution cast films. This gel film can be considered as a composite material with superparamagnetic property.

Authors' contributions

JC conducted the experiments to synthesize of the PVA magnetic film, characterization of the film by electron microscopy and magnetometry and prepared the manuscript. YH supervised the study and planned for the write up of the whole study in the form of an article for publication. CJC reviewed the manuscript and overall evaluation of the paper. All authors read and approved the final format of the paper.

Acknowledgements

The work was sponsored by a grant from the Center for Materials Research and Technology (MARTECH) at Florida State University.

References

1. Venkatraman SS, Murdock TO, Pudjianto S: **Pharmaceutical hydrogel formulations, and associated drug delivery devices and methods.** *United States Patent 6,039,977* 1997.
2. Osada Y, Gong J: **Soft and Wet Materials: Polymer Gels.** *Adv Mater* 1998, **10**:827-837.
3. Zrinyi M, Barsi L, Buki A: **Ferrogel: a new magneto-controlled elastic medium.** *Polym Gels Netw* 1997, **5**:415-427.

4. Lin H, Watanabe Y, Kimura M, Hanabusa K, Shirai H: **Preparation of magnetic poly(vinyl alcohol) (PVA) materials by in situ synthesis of magnetite in a PVA matrix.** *J Appl Polym Sci* 2003, **87**:1239-1247.
5. Sauzedde F, Elaissari A, Pichot C: **Hydrophilic magnetic polymer latexes. I. Adsorption of magnetic iron oxide nanoparticles onto various cationic latexes.** *Coll Polym Sci* 1999, **277**:846-855.
6. Chatterjee J, Haik Y, Chen CJ: **Biodegradable magnetic gel: synthesis and characterization.** *Coll Polym Sci* 2003, **281**:892-896.
7. Vassiliou JK, Mehrotra V, Russell MV, Giannelis EP: **Magnetic and optical properties of γ -Fe₂O₃ nanocrystals.** *J Appl Phys* 1993, **73**:5109-5116.

Publish with **BioMed Central** and every scientist can read your work free of charge

"BioMed Central will be the most significant development for disseminating the results of biomedical research in our lifetime."

Sir Paul Nurse, Cancer Research UK

Your research papers will be:

- available free of charge to the entire biomedical community
- peer reviewed and published immediately upon acceptance
- cited in PubMed and archived on PubMed Central
- yours — you keep the copyright

Submit your manuscript here:
http://www.biomedcentral.com/info/publishing_adv.asp

